


AM 0/8-680 Coating

Client : Quality Control Argex
 0032/32.50.15.15

lab	Quality Control Argex 0032/32.50.15.15
Aggregate Size	0/8 mm
Certifications	EN 13055 : . (1/01/2004)

Essential char. - performance	Minimum	Average	Maximum	Declared	Standard
Particle Shape		Mix			EN 13055
Loose Bulk Density (+- 15% of declared value)	580	778 kg/m ³	780	680	EN 1097-3
Oven-Dried Particle Density (+- 15% of declared value)	1000	1197 kg/m ³	1300	1150	EN 1097-6 Filtermethod
Freezing & Thawing Resistance		2.3 %	3.3		NF P18-545
Volume Stability		0.22 %	0.50		EN 1367-8
Water Content (from silo)	0.0	7.8 %	14.0		EN 1097-5
Water Absorption 2h	6.00	9.03 %	12.00		EN 1097-6 Filtermethod
Water Absorption 30'	5.00	7.34 %	11.00		EN 1097-6 Filtermethod
Water Absorption 5'	4.00	5.87 %	10.00		EN 1097-6 Filtermethod
Active alkalines content (Na ₂ O eq.)		0.044 %			LPC 37
Alkali - reactivity (qualification)		No Reactive (NR)			FD P18-542
Chloride		0.005 %	0.010		EN 1744-1
Total Sulphur		0.29 %	0.55		EN 1744-1
Acid-Soluble Sulfate		0.150 %	0.500		EN 1744-1

Grading (EN 933-1)				
sieve (mm)	mini	% passing	maxi	Declared
0.000		0.0		
0.063		4.1		
0.125		7.1		
0.250		9.7		
0.500		12		
1.000		18		
2.000		32		
3.150		43		
4.000		50		
6.300		78		
8.000	90	98	100	
10.000		100		

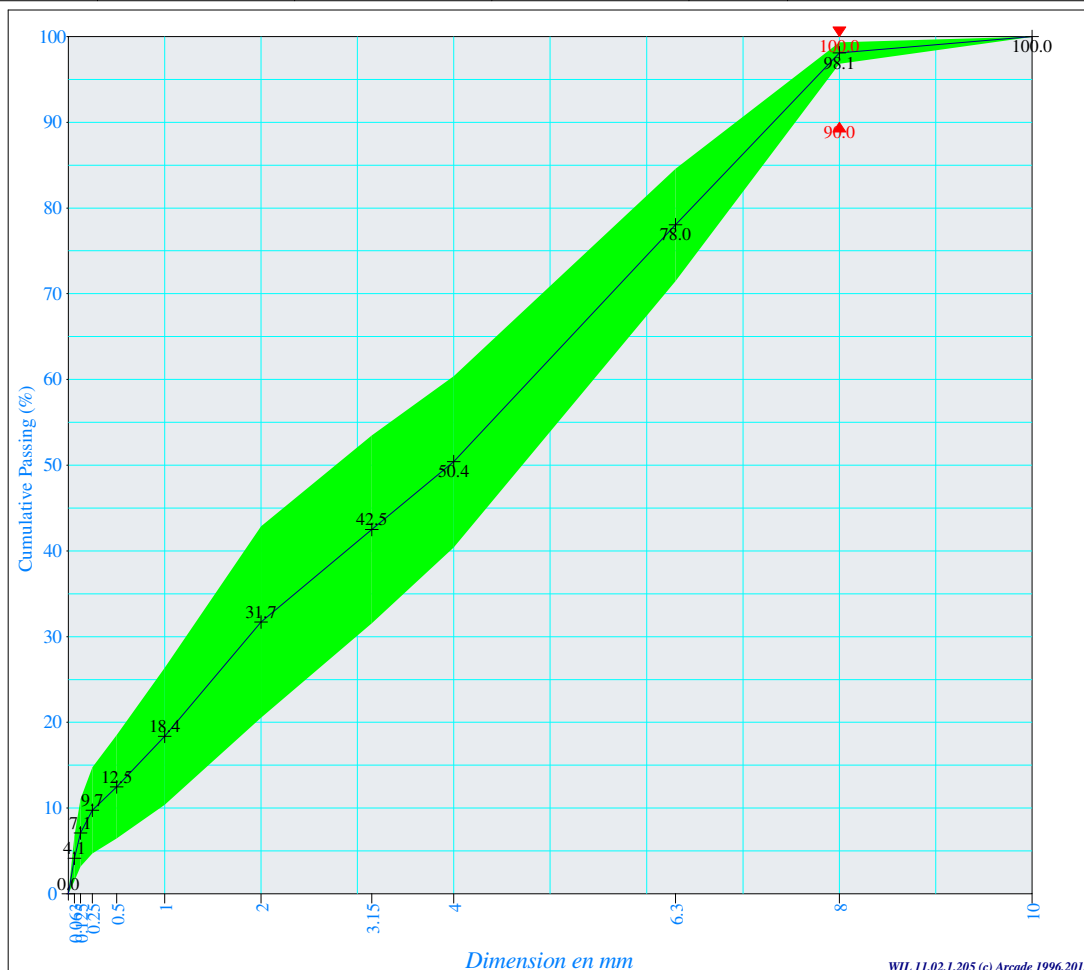

WIL 11.02.1.205 (c) Areade 1996,2015